

## ***X-RAY MICRO-TOMOGRAPHY APPLIED TO NASA'S MATERIALS RESEARCH: HEAT SHIELDS, PARACHUTES AND ASTEROIDS***

Francesco Panerai<sup>\*1</sup>, Arnaud Borner<sup>2</sup>, Joseph C. Ferguson<sup>3</sup>, Nagi N. Mansour<sup>4</sup>, Eric C. Stern<sup>4</sup>, Harold S. Barnard<sup>5</sup>,  
Alastair A. MacDowell<sup>5</sup> & Dilworth Y. Parkinson<sup>5</sup>

<sup>1</sup>AMA Inc. at NASA Ames Research Center, United States

<sup>2</sup>UIUC at NASA Ames Research Center, United States

<sup>3</sup>STC at NASA Ames Research Center, United States

<sup>4</sup>NASA Ames Research Center, United States

<sup>5</sup>Lawrence Berkeley National Laboratory, United States

**Keywords:** porous media, textiles, meteorite materials

**Summary:** X-ray micro-tomography is used to support the research on materials carried out at NASA. The technique is applied to a variety of applications, including the ability to characterize heat shield materials for planetary entry, to study Earth-impacting asteroids, and to improve broadcloths of spacecraft parachutes. From micro-tomography images, relevant morphological and transport properties are determined and validated against experimental data.

### **1. INTRODUCTION**

In building spacecraft, satellites, space suits or any other system to explore our Universe, NASA adopts advanced materials with tailored properties to handle the extreme environmental conditions of outer space. As the properties and performance of these materials are determined by their 3D microstructure, imaging materials in 3D, at the scale of their constituents, is an important part of their characterization, design and analysis. X-ray micro-tomography (micro-CT) is an established technique to non-destructively characterize material structures at scales varying from the sub-micron to the centimeter. Synchrotron sources of x-rays allow micro-tomography to be applied to a large variety of materials and enable the use of environmental cells where the materials can be subjected to actual operational conditions, such as thermal and mechanical loads or reactive atmospheres.

In this paper, we illustrate three applications of x-ray micro-CT to research on advanced materials of interest to NASA. The first application is the study of high temperature fibrous media, used in low-density thermal protection systems (TPS) for atmospheric entry vehicles. Critical to this class of materials is the ability to model with high-fidelity the physical processes occurring in their porous structure, such as heat transfer, chemical phenomena and flow transport. Secondly, micro-CT is applied to characterize textiles of parachutes used for slowing down spacecraft during atmospheric descent. From the 3D images, parachute fabric permeability is computed. The third application concerns the analysis of meteoritic materials. In an effort to utilize NASA's design tools for entry spacecraft to predict energies and dynamics of Earth-impacting asteroids, tomographic imaging of meteorites is used to characterize their microstructure and their fracture upon atmospheric impact.

### **2. METHODS**

Experiments were performed at the beamline 8.3.2 of the Advanced Light Source (ALS) synchrotron facility at Lawrence Berkeley National Laboratory. The capabilities of the facility are described with detail in [1]. For this work, we used x-ray energies between 15 and 18 keV to image low-density fibrous materials and white light for metal-rich, dense meteorites. Using a 2560×2160 pixels detector and an Optique Peter microscope, a voxel size of ~0.65 μm was obtained with a 10× magnification lens in order to resolve fibrous structures. A 5× magnification, providing a voxel size of ~1.3 μm, was instead used for imaging meteorite materials. During the scans a total of 1024 radiographs were acquired and reconstructed using the *TomoPy* software. The *Avizo* package was used for segmentation and visualization, while material properties and simulations were performed using software described in [2-3], as well as the Porous Material Analysis (*PuMA*) code, presented in a companion paper.

---

\* e-mail: francesco.panerai@nasa.gov

### 3. RESULTS

Micro-tomography images of the different materials investigated are shown in Fig. 1. Morphological information at the microscale can be characterized for both fibrous and dense materials. Fig. 1(a) shows temperature and velocity fields within a highly porous carbon fiber material. Heat transfer is simulated using a finite difference method that allows the effective material conductivity to be computed from the conductivity of the constituting phases [2]. The computations show that, due to the high porosity ( $> 85\%$ ), different conductivities of the gas phase can result in up to 20% differences in the effective material conductivity [2]. The flow-field is computed using the Direct Simulation Monte Carlo (DSMC) method, which accounts for slip effects occurring in porous heat shield material operating at high temperature and low pressures. It is shown that the DSMC method applied to micro-CT is able to predict the Klinkenberg permeability of the material at high temperature. Simulations at temperatures between ambient and 1500 K show an excellent agreement when compared with laboratory measurements in a high temperature flow-tube setup [3].

Porosity and permeability are also computed based on high-resolution tomography of the nylon ripstop weave of a supersonic parachute, shown in Fig. 1(b). Values are to be compared for relaxed fabrics and weaves under biaxial tension that simulates an actual operational load for the deployed parachute.


The micro-CT of the Tamdakht H5 Chondrite Meteorite (Fig. 1(c)) reveals a heterogeneous micro-structure composed of a porous glassy crust, high-density Fe- and Ni-rich grains, and olivine and peroxine grains immersed in a lower density matrix with a large concentration of micron-size fractures. The propagation of those fractures is to be studied through in-situ experiments in the ALS 8.3.2 beamline where the meteorite material is subjected to compression loads until failure.

#### Acknowledgements

This work was supported by the NASA Entry System Modeling (ESM) project and the NASA Asteroid Threat Assessment Project (ATAP). The Advanced Light Source is supported by the Director, Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231.

#### References

- [1] A.A. MacDowell, D.Y. Parkinson, et al. & A.J. McElrone, X-ray micro-tomography at the Advanced Light Source, *Proc. SPIE 8506, Developments in X-Ray Tomography VIII*, 850618, 2012.
- [2] F. Panerai, J.C. Ferguson, J. Lachaud, A. Martin, M.J. Gasch & N.N. Mansour. Micro-tomography based analysis of thermal conductivity, diffusivity and oxidation behavior of rigid and flexible fibrous insulators, *Int. J. Heat Mass Transfer*, 108, 801-811, 2017.
- [3] A. Borner, F. Panerai & N.N. Mansour. High-temperature permeability of fibrous materials using direct simulation Monte Carlo, *Int. J. Heat Mass Transfer*, 106, 1318-1326, 2017.

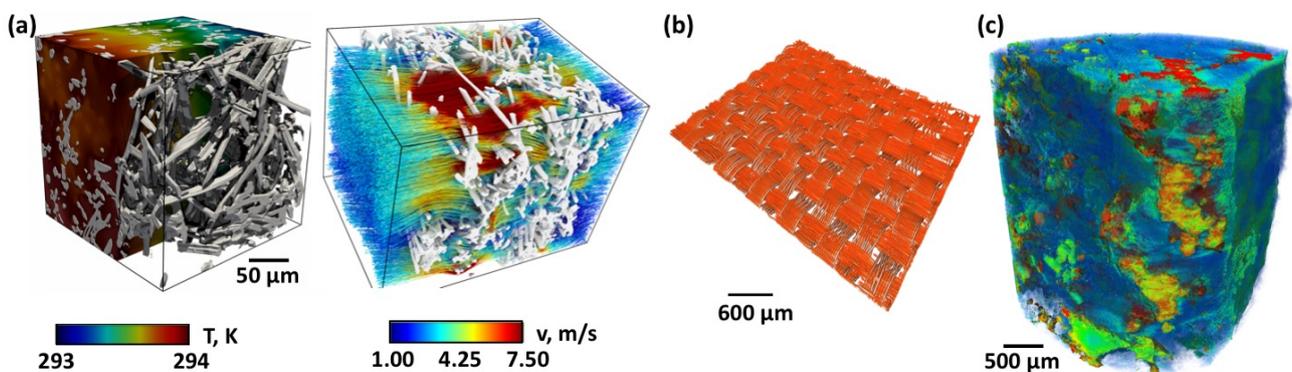

**Figure 1:** (a) Temperature (left) and velocity (right) fields in a porous carbon fiber insulator. (b) Micro-tomography of a parachute fabric. (c) Micro-tomography of the Tamdakht meteorite. The color map shows areas of different density within the material (red is denser).